



ISTITUTO
GIORDANO



Istituto Giordano S.p.A.
Via Rossini, 2 - 47814 Bellaria-Igea Marina (RN) - Italy
Tel. +39 0541 343030 - Fax +39 0541 345540
istitutogiordano@giordano.it - www.giordano.it
Cod. Fisc./P.Iva 00 549 540 409 - Cap. Soc. € 1.500.000 i.v.
R.E.A. c/o C.C.I.A.A. (RN) 156766
Registro Imprese di Rimini n. 00 549 540 409

TEST REPORT No. 298675

Place and date of issue: Bellaria-Igea Marina - Italy, 10/10/2012

Customer: I PROFILI S.n.c. di Ceccato Nicola & C. - Via Alinate, 62 - 35121 PADOVA - Italy

Date test requested: 07/09/2012

Order number and date: 57390, 10/09/2012

Date sample received: 21/09/2012

Test date: 24/09/2012

Purpose of test: tensile testing machine in accordance with standard UNI EN ISO 6892-1:2009

Test site: Istituto Giordano S.p.A. - Via Erbosa, 74 - 47043 Gatteo (FC) - Italy

Sample origin: sampled and supplied by the Customer

Identification of sample received: No. 2012/1977


Description of sample*


The test sample comprises 1 galvanised steel sheet of thickness 0,6 mm.

Normative References

The test was carried out according to the requirements of standard UNI EN ISO 6892-1:2009 dated 08/10/2009 "Materiali metallici - Prova di trazione - Parte 1: Metodo di prova a temperatura ambiente" (*"Metallic materials - Tensile testing - Part 1: Method of test at room temperature"*).

(*) according to that stated by the Customer.

Comp. AV
Revis. 

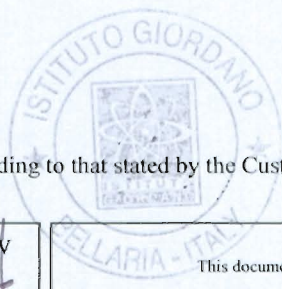

This test report consists of 2 sheets.

This document is the English translation of the test report No. 298675 dated 10/10/2012 issued in Italian.

Date of translation: 19/10/2012.

Sheet
1 of 2


Test results

Test piece ID	Size		Area [mm ²]	Elongation after fracture A ₈₀ [%]	Yield strength f _y [N/mm ²]	Tensile strength f _t [N/mm ²]
	[mm]					
1A	0,55	× 20,10	11,05	28,10	356,24	410,22
2A	0,55	× 20,12	11,07	17,12	350,35	408,64
3A	0,55	× 19,99	10,99	/	349,36	406,39
4B	0,55	× 20,37	11,20	20,80	353,90	406,61
5B	0,55	× 20,09	11,05	24,00	346,87	402,10
6B	0,55	× 20,39	11,22	27,50	355,35	406,10


Note: Test carried out with universal testing machine using method A (strain rate control).



Test Technician
(Dott. Ing. Michele Ianniello)



Head of Building Materials
Laboratory
(Dott. Geol. Gianluca Ferraiolo)



Managing Director

L'AMMINISTRATORE DELEGATO
Dott. Ing. Vincenzo Iommi

